



Synthesis and characterization of nano zinc peroxide photocatalyst for the removal of brilliant green dye from textile waste water.

Prashant L. Chaudhari*, Pallavi C. Kale

Department of Chemical Engineering, BharatiVidyapeeth University College of Engineering, Pune, India

Abstract : The zinc peroxide nanoparticles were synthesized by using oxidation-hydrolysis-precipitation process. With zinc acetate as a predecessor, Hydrogen peroxide used as a oxidizing agent and polyethylene glycol 200 (PEG 200) was used as a surface modifier. Characterization of zinc peroxide nanoparticles was done by X-ray diffraction [XRD], Fourier transformer infra red [FTIR] and transmission electron microscope [TEM]. The parameters like pH, dye concentration, dosage of nanoparticle catalyst, temperature and contact time were studied for the application of Zinc peroxide nanoparticle as a catalyst for removal of a Brilliant green dye from synthetic sample. Excellent degradation efficiency of brilliant green dye was 86.68% achieved by zinc peroxide with PEG as a catalyst and 84.16% achieved by zinc peroxide without PEG as a catalyst at 120 min of photo catalytic reaction. The maximum degradation efficiency of brilliant green dye (86.68%) was achieved at the optimum operational conditions: initial concentration of dye 9mg/l, catalyst dosage of 200 mg, pH of solution will be in between 6-7.

Keywords : Zinc peroxide nanoparticles, Brilliant green dye, Zinc oxide, Textile waste.

Introduction

The consumption of dyes was highly increased by textile industries in recent years and because of this scenario large amount of coloured wastewater from such industries create serious problems to the environment. From the last few years, colour removal from textile dyeing effluents has been the target of great attention, the reason is not only its toxicity but mainly due to its aesthetic effect and this cause even at lower concentrations, comparing to many other chemicals found in wastewater. Because of dyes large amount of surface water get polluted. More than 10000 dyes are available in textile business sector around the world¹. Most of the dyes are not get easily degradable, just only 1 mg/lit dye concentration can also make surface water polluted.

For clean and safe water it is necessary to remove dyes and because of this the quality of all life improved. For all the leaving organisms water is very important part but water is easily get polluted because of the many dyes. Small amount of dye concentration in water also affect surface water, and it is very dangerous to environment. Photocatalytic decolourization requires light energy to activate nanoparticles to for decolorization dyes and it produces less toxic byproducts. The waste water of textile and dye industries are considered to be the most polluting industries and highly hazardous to aquatic living being because they cause serious damage to the surrounding environment^{2,3}. So it is very important to treat the waste water. There are many methods techniques for treatment of waste water such as adsorption^{4,5}, coagulation^{6,7}, ion flotation⁸ and sedimentation⁹. All these techniques are versatile and useful, but they all produce secondary waste which needs

treatment further. Many methods widely used for the removal of dyes but adsorption is low in cost but it is not reusable and produce toxic waste. Another set of techniques that are relatively new, more powerful and very efficient called Advance Oxidation Processes (AOPs) has been developed and employed to treat dye-contaminated wastewater effluent¹⁰.

Brilliant green (BG) is a member of triphenyl methane dyes which are extensively used in textile industry for dyeing nylon, wool, cotton, silk as well as for coloring of oils, fats, waxes, plastics and varnishes. BG is considered as highly toxic to both humans and animals since it causes irritation of respiration and gastrointestinal tracts leading to diarrhea and vomiting. Many countries banned on BG due to its carcinogenic nature^{11,12,13}. Molecular formula of BG is $C_{27}H_{34}N_2O_4S$ (Mol. Wt = 482.62 g/mole)¹⁴. On the other hand, heterogeneous photocatalysis under visible light offers distinct advantages besides being an energy saving green technology.

Zinc peroxide is mostly produced by adding one of the following: Zinc oxide; Zinc hydroxide; Zinc nitrate; Zinc chloride, Zinc carbonate in a solution of hydrogen peroxide, with an additional light energy as a source^{15,16}. Nanocatalyst of zinc peroxide can be used as predecessor for preparation of nanoparticles zinc oxide. The surface modifier is used as a polyethylene glycol 200 (PEG 200). To analyze the efficiency of the PEG(200) as nanoparticle stabilizer, the nanoparticle of zinc peroxide has been produced in two different types: zinc peroxide without PEG200 (ZnO_2 WOPEG) and zinc peroxide with PEG200 (ZnO_2 WPEG)¹⁷. In present work, synthesis of zinc peroxide had done by using zinc acetate, hydrogen peroxide and polyethylene glycol. It used for degradation of brilliant green dye.

Experimental

Materials:

All the chemicals used in this experiment are A.R. grade and brought from reputed companies. Zinc acetate dehydrate [$Zn(CH_3COO)_2 \cdot 2H_2O$] was brought from the High purity laboratory chemicals private limited, Mumbai-400002; 50% hydrogen peroxide aqueous solution (H_2O_2); PEG 200 [$H(OCH_2CH_2)_nOH$]; and sodium hydroxide [NaOH] were procured from Sigma Life Science. Brilliant green dye was brought from merck specialities private limited Mumbai.

Preparation of ZnO_2 nanoparticle solution:

Zinc peroxide nanoparticles were prepared by dissolving 3 gm of elemental Zinc acetate dehydrates in 30 mL of deionized water. To the resulting dispersion 120ml of PEG 200 and 9 ml of H_2O_2 (50%) were added slowly. This complete procedure carried out at room temperature and continuous stirring was kept constant for all the experiments. After the continuous stirring of two hours a clear and colorless solution is converted into yellow colour^[21]. In this process different type of stirring process were used as shown figure 1. It observed that ultrasound sonication stirring got maximum yield as compared to other stirring process.

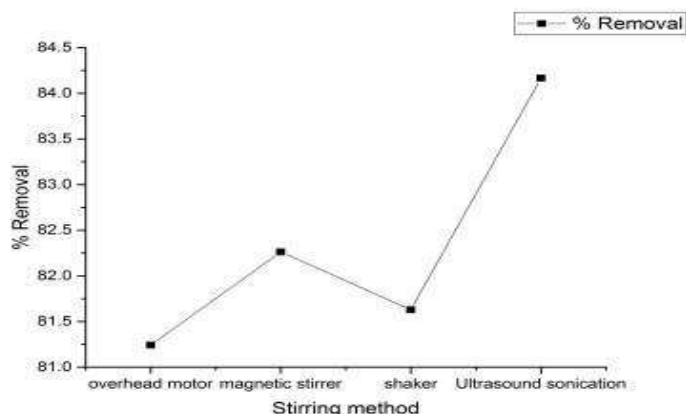


Figure 1: Different type of stirring process

Preparation of ZnO₂ nanoparticle powder:

After continuous stirring of 2 hours, add NaOH solution of 4N was added to form a basic medium. After addition of the 4N NaOH, the white color precipitate produced. Add NaOH upto pH value of solution was 11.5 obtained.

Then by centrifuge process, white precipitate was separated from the solution mixture and after the centrifugation process slurry type mixture formed. Then mixture washed at least five to six times by NaOH solution. Finally maintain the pH of the residue water 8.4 by applying 10-12 additional washes of distilled water. The white colored precipitate was dried at 80°C for two hours in an oven¹⁷.

Removal of brilliant green dye:

A stock solution (1,000 mg/l) was prepared by dissolving a 1gm of dye in 1 litre distilled water and was diluted to the required initial concentrations. Batch experiments were carried out to study the effect of various parameters such as the pH, adsorbent dose, temperature, contact time and initial brilliant green dye concentration. To study the effect of these parameters, initial dye concentration (1 to 15 mg/l), adsorbent dosage (0.1 - 1 g/100 ml), pH (1 to 12), contact time of 10 to 180 min and agitation rate (150 rpm), were considered. The pH of solutions measure by using pHmeter. For each experimental run, 100 ml of dye solutions with different concentration and at a known pH and a known amount of the adsorbent were taken in a 500 ml conical flask. For investigation of the effect of initial dye concentration. The samples were mixed by use of a magnetic stirrer at a constant speed of 150 rpm in presence of UV lamp. In order to separate the adsorbents from the aqueous solutions, all samples were centrifuged and after that the samples was measured by UV spectrophotometer. Ultra violet (UV)-visible spectra have been acquired between 200 and 800 nm with a UV-Visible spectrophotometer. Dye concentration in solutions measured by UV-Visible spectrophotometer at $\lambda_{max} = 720$ nm for brilliant green dye. The removal efficiency of dye was calculated using the following equation:

$$\% \text{ Removal} = \frac{(C_0 - C_t)}{C_0} \times 100$$

Where C_0 and C_t (mg/l) are the initial dye concentration and concentration at time (t), respectively¹⁸.

Characterization

X-ray diffraction analysis:

Figure 2a and 2b shows XRD diffraction pattern of Zinc peroxide nanoparticles. Figure 2 shows the crystal structure and phase purity of the ZnO₂. The peaks are indexed as 31.8° (452), 36.2° (626), 47.5° (168), 56.7° (233), 62.8° (196), 66.06° (200), 68° (169) and 69° (109) respectively. From this it is proved that pure nanoparticles of zinc peroxide were synthesized¹⁹.

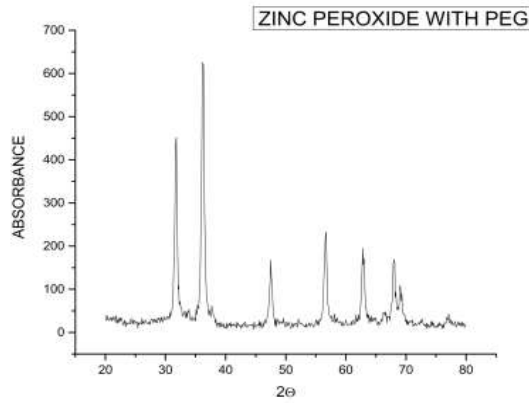


Figure2 (a):XRD patterns of zinc peroxide with PEG nanoparticle

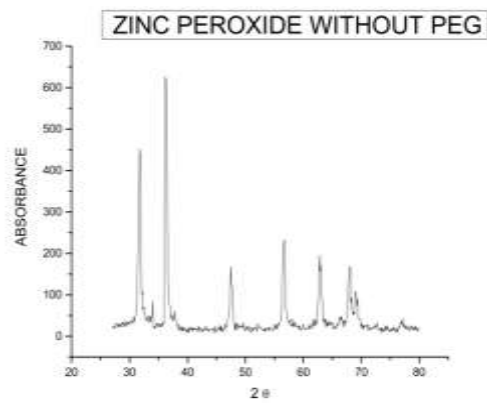


Figure2 (b): XRD patterns of zinc peroxide without PEG nanoparticle



Figure3 (a):XRD patterns of recycled(1st cycle) Zinc peroxide nanoparticle without PEG

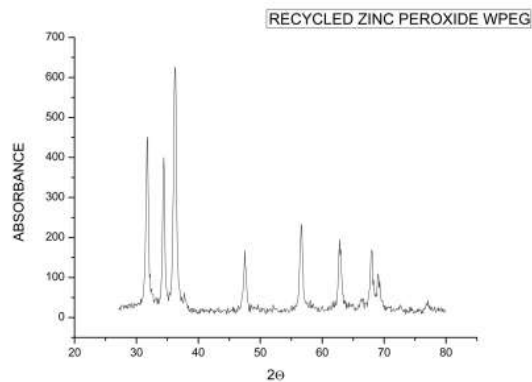


Figure3 (b):XRD patterns of recycled(1st cycle) zinc peroxide nanoparticle with PEG

Figure 3a and 3b shows that zinc peroxide sample after thermal treatment converted into Zinc oxide nanoparticles. The peaks are indexed as 31.8° (452), 34.4° (400), 36.2° (626), 47.5° (168), 56.7° (233), 62.8° (196), 66.06° (200), 68° (169) and 69 (109) respectively. From this it is proved that pure nanoparticles of zinc oxide were synthesized²⁰.

Transmission Electron Microscopy:

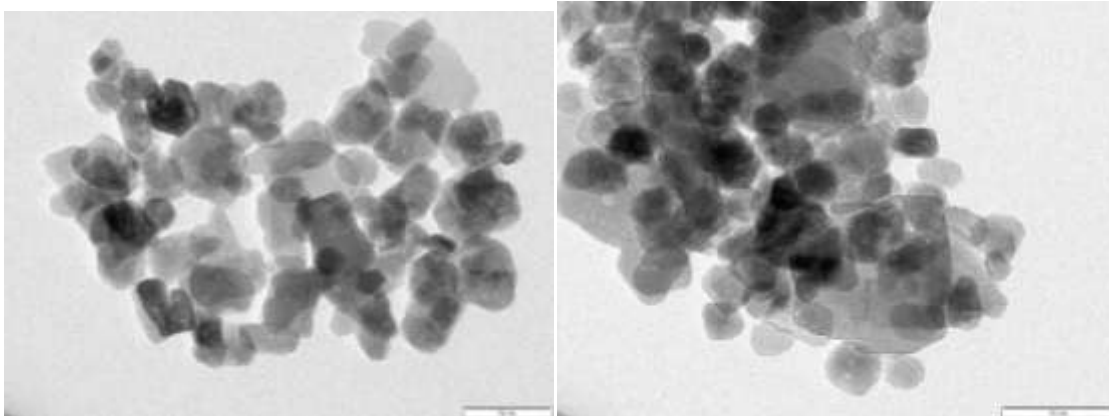


Figure4 (a):TEM of ZnO₂ without PEG

Figure4(b): TEM of ZnO₂ with PEG

Figure 4 (a & b) show the TEM images of ZnO₂ nanoparticles. TEM analysis was done at IIT, Powai using TEM CM 200 of the PHILIPS company. The morphology and microstructure of the zinc peroxide nanoparticles was obtained by using TEM analysis.

TEM observations of the Zinc peroxide without PEG and zinc peroxide with PEG, examine a slight difference between the agglomeration shapes as shown in figure 4a. Zinc peroxide without PEG formed dense agglomerates, whereas in figure 4b. zinc peroxide with PEG created smaller size agglomerates.

FTIR spectroscopy:

Figure 5 (a& b) shows FTIR spectra of nanoparticles zinc peroxide. Metal oxides generally give absorption bands in fingerprint region i.e. below 1000 cm⁻¹ arising from inter-atomic vibrations. Absorption peaks are obtained at 3431 and 1590 cm⁻¹ to the stretching vibration of the O-H bond and the bending vibration of H-O-H from water molecules respectively. The peak at 489 cm⁻¹ shows the absorption band of the samples.²¹

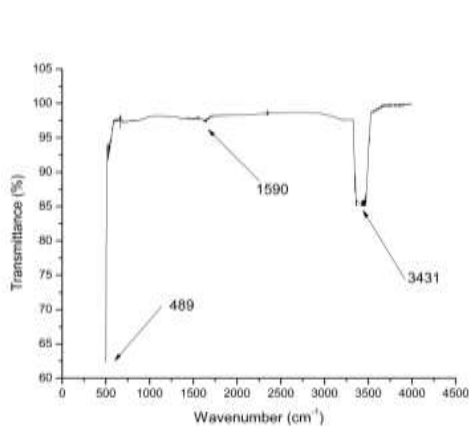


Figure5(a):FTIR of ZnO₂with PEG

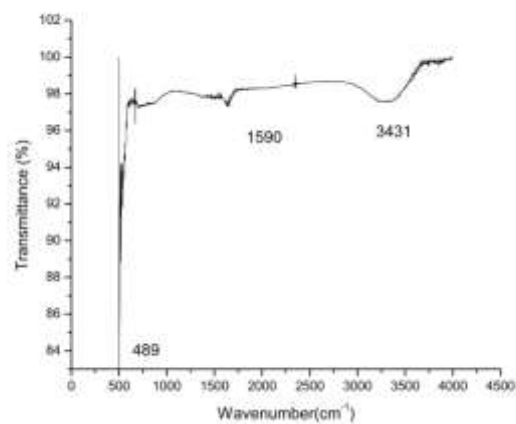


Figure5(b): FTIR of ZnO₂without PEG

Result and Discussions:

Effect of doses and time:

The effect of contact time on % removal of Brilliant green dye (5 mg/litre) at different dosage of nanoparticles of zinc peroxide as shown in figure.6 and 7. The plots prove that as the dosage of nanoparticles zinc peroxide with PEG and zinc peroxide without PEG increased from 100 to 1000 mg, the maximum % decolourization of brilliant green dye was 83.6028% and 82.17198% respectively shown in figure 7. Thus, maximum decolourization achieved at 120 min as shown in figure 6²²

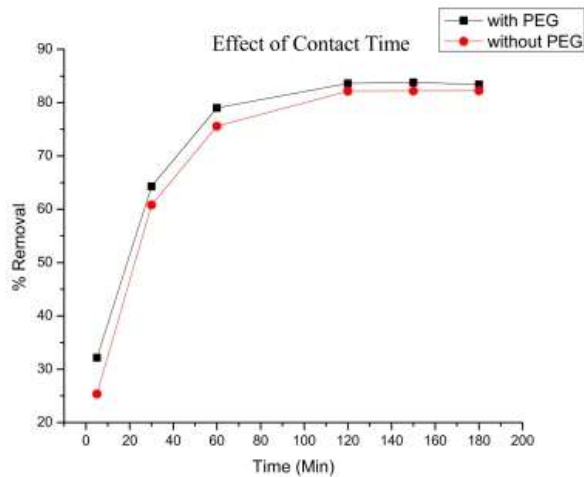


Figure6:Effect of contact time on removal of BG dye by using nanocatalyst as zinc peroxide with PEG and zinc peroxide without PEG (Dye concentration= 5 mg/lit, Temperature-30°C,pH-6.5, Catalyst dose-200mg)

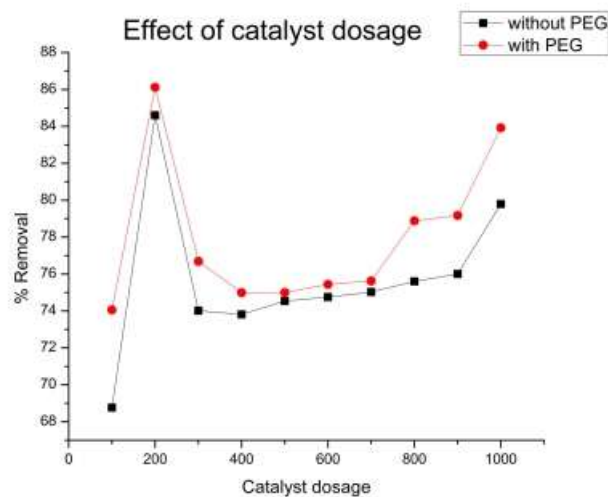


Figure7:Effect of catalyst dosage on removal of BG dye by using nanocatalyst as a zinc peroxide with PEG and zinc peroxide without PEG(Dye concentration-5 mg/lit, Temperature-30°C,pH-6.5, Time- 120 min)

Effect of initial dye concentration:

As shown in figure 8, the effect of Brilliant green dye concentration was studied by varying concentration from 1 to 15 mg/L, the % removal of dye efficiency got decreased for the same amount of nanoparticle zinc peroxide concentration. The dye decolourization study was performed using 200 mg/100ml nanoparticle by taking 9 mg/litre of the dye for 120 min and pH of solution was 6. Figure 8 shows the % removal of the dye solution after decolourization. The absorbance of the dye solution has remained constant after 9 mg/litre at wavelength (622.4 nm) disappearing completely. The maximum % decolourization was observed at 9mg/L for zinc peroxide with PEG it was 86.68623% and for zinc peroxide without PEG it was 84.16476% (for 120 min).

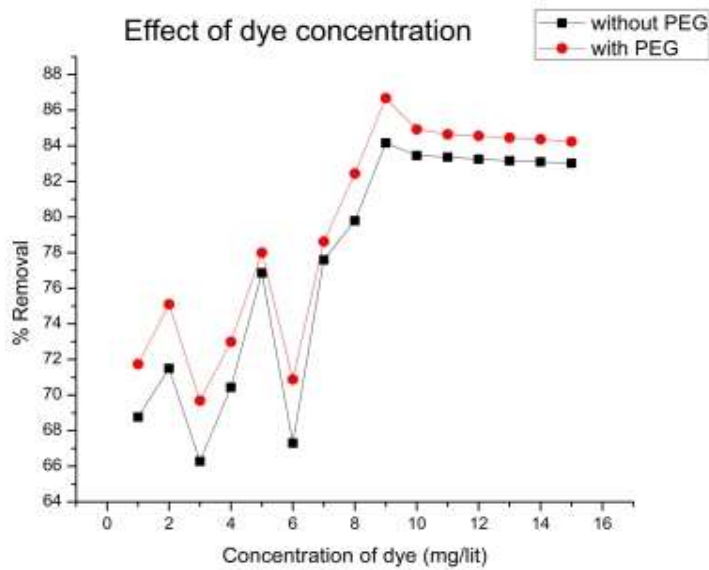


Figure8:Effect of dye concentration on removal of BG dye using nanocatalyst as a zinc peroxide with PEG and zinc peroxide without PEG (Temperature-30°C,pH-6.5, Catalyst dose-200mg, Time- 120 min)

Effect of pH:

In this work, we studied the effect of pH on dye degradation in the range of 3–12 pH Solutions were prepared with a dye concentration of 9 mg/l and their pH was adjusted using 0.1 N HCl and 0.1 N NaOH. The used catalyst dose was 200mg and maximum time was 120 min. Figure. 9 shows % removal of the dye at different pH values. It can be seen that maximum % removal with zinc peroxide with PEG was observed at pH 6 (85.43041 % in 120 min) and zinc peroxide without PEG was observed at pH 6 (83.25879 % in 120 min)

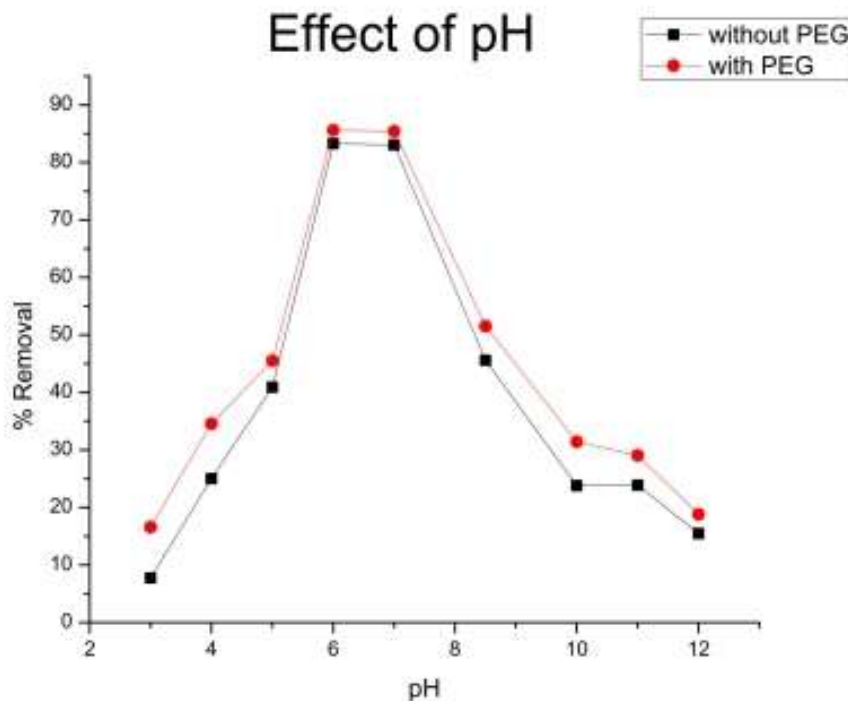


Figure9:Effect of pH on removal of BG dye by using nanocatalyst as a zinc peroxide with PEG and zinc peroxide without PEG (Dye concentration-5 mg/lit, Temperature-30°C, Catalyst dose-200mg, Time- 120 min)

Effect of temperature:

Effect of temperature on the photocatalytic removal of brilliant green dye was investigated in the range of temperatures 25°C to 55°C. The used catalyst dose was 200mg, and the pH value of solution was kept 6 and dye concentration 9 g/ litre. The photocatalytic dye removal were increased with as increase of the reaction temperature to approach 91.84871% for the used dye aqueous solution at temperature 55°C, and the obtained results are shown in Figure 10.


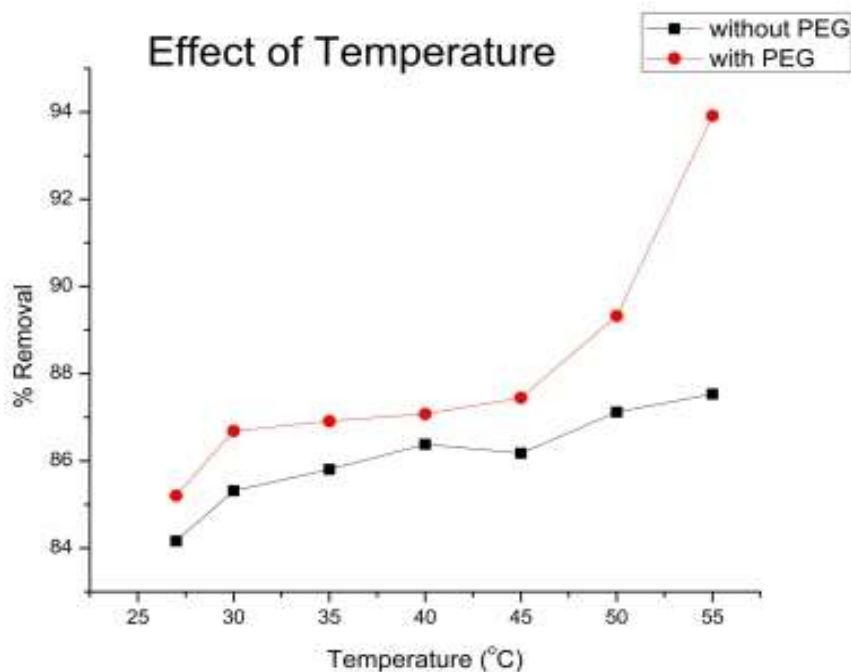


Figure10: Effect of temperature on removal of BG dye by using nanocatalyst as zinc peroxide with PEG and zinc peroxide without PEG (Dye concentration-5 mg/lit,pH-6.5, Catalyst dose-200mg, Time- 120 min)

Recycle of the used catalyst zinc peroxide:

Reuse of the catalyst which was used in the removal of Brilliant green from the wastewater was performed using solvents to wash the used catalyst with distilled water many times, then it was dried at 300°C in oven for ten hours to remove the sticking molecules of dye¹⁷.



The obtained material was converted from zinc peroxide to zinc oxide and it was characterized by XRD test as shown in figure. 3.a. and 3.b. then obtained zinc oxide was used in the removal of brilliant green dye using the same optimum conditions that were used for zinc peroxide and the obtained results are shown in Figure 11. From these figure it was found that the first use catalyst and the second use gave the removal efficiency for this dye 86.68623 and 74.29609 respectively. After fifth time of use, the efficiency of % removal was decreased upto 47.2202%. The % removal of recycled catalyst goes on decrease as per the every cycle.

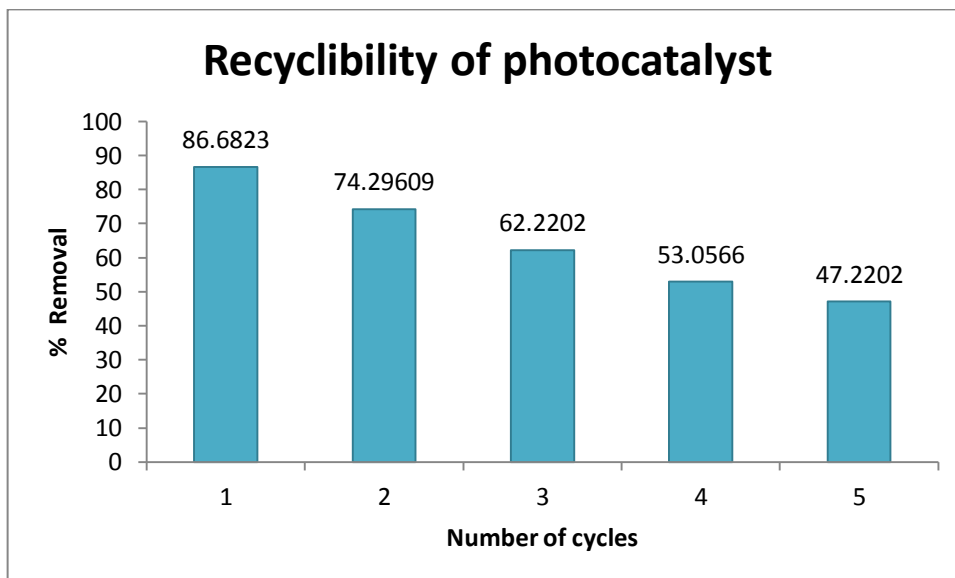


Figure11: Recyclibility of photocatalyst

Conclusion:

Stabilised ZnO₂ nanoparticles were synthesized by using ultrasound sonication process. For characterization different techniques were applied (XRD, TEM, FTIR). The photocatalytic decolourization of Brilliant green was achieved successfully by two catalyst i.e. zinc peroxide with PEG and zinc peroxide without PEG. From the result we come to know that the photocatalytic decolourization of dye with nanoparticles of catalyst zinc peroxide depend on the concentration of dye, dosage of photocatalytic nanoparticles, Contact time, pH of solution, Temperature of solution. It was found that the optimal amount of catalyst used was 200mg/lit. It has been observed that at 10 mg/lit maximum decolourization occurs. The decolourization is favored in neutral solution. The optimal time to be required was found 120 min.

The recycling of zinc peroxide can be performed up to five cycles. After use of first cycle the heat treatment was done on used zinc peroxide and after that zinc peroxide was converted into zinc oxide.

Acknowledgements:

The authors would like to express sincere thanks to Dr. Anandbhalerao, principal Bharati Vidyapeeth University College of Engineering, Pune for the use of laboratory facilities. We are also thankful to Dr. P. V. Chavan, Dr. S. M. Jadhav, Prof. K. S. Kulkarni for their continuous encouragement and technical guidance.

References:

1. V.V. Dawkar, U.U. Jadhav, S.U. Jadhav and S.P. Govindwar, Biodegradation of disperse textile dye brown 3rel by newly isolated bacillus sp. vus, Journal of applied microbiology 2008, 105: 14-24.
2. J. McCann, B. N. Ames, Detection of carcinogens as mutagens in the salmonella/microsometest: assay of 300 chemicals:discussion, Procnatlacadsciua 1976,73: 950-954.
3. Michael R. Hoffmann, Scot T. Martin, Wonyong Choi, and Detlef W. Bahneman, Environmental Applications of Semiconductor Photocatalysis, Chemical reviews 1995,95:69-96.
4. N. Nasuha, B. H. Hameed, A. T. M. Din, Rejected tea as a potential low-cost adsorbent for the removal of methylene blue, Journal of hazardous materials, 2010,175;1-3:126-132.
5. M. A. Rauf, S. M. Qadri, S. Ashraf, K. M. Almansoori, Adsorption studies of toluidine blue from aqueous solutions onto gypsum, Chemical engineering journal, 2009, 150:90-95.

6. A.L. Ahmad, S.W. Puasa , Reactive dyes decolourization from an aqueous solution by combined coagulation/micellar enhanced ultrafiltration process, *Chemical engineering journal*, 2007,132: 257-265.
7. M. Riera Torres, C. Gutiérrez Bouzán, M. Crespi, Combination of coagulation-flocculation and nanofiltration techniques for dye removal and water reuse in textile effluents, *desalination*, 2010, 252: 53- 59.
8. Kamal Shakir , Ahmed Faouzy Elkafrawy, Hussein Fouad Ghoneimy Shokry Gad Elrab Beheir, Mamdoh Refaat, Removal of rhodamine b (a basic dye) and thoron (an acidic dye) from dilute aqueous solutions and wastewater simulants by ion flotation, *water research*, 2010,44:1449-1461.
9. Salim Zodi, Olivier Potier, François Lopicque, Jean-Pierre Leclerc, Treatment of the industrial wastewaters by electrocoagulation: optimization of coupled electrochemical and sedimentation processes, *desalination*, 2010,261:186-190.
10. M. A. Rauf, S. S. Ashraf, Application of advanced oxidation processes (aop) to dye degradation an overview, In: A. R. Lang, Ed., *Dyes and Pigments: new research*, Nova science publishers, Inc., Hauppauge, 2009.
11. P.R. Gogate, G. S. Bhosale, Comparison of effectiveness of acoustic and hydrodynamic cavitation in combined treatment schemes for degradation of dye wastewaters, *Chemical Engineering Processing*, 2013,71: 59-69
12. KaisaKlemola, John Pearson, Pirjo Lindstrom-Seppa, Evaluating the toxicity of reactive dyes and dyed fabrics with the hacat cytotoxicity test, *AUTEX Research Journal*, 2007,7; 217-223
13. B.K. Nandi, A. Goswami, M. K. Purkait, Adsorption characteristics of brilliant green dye on kaolin”, *Journal of Hazardous Materials*,2009 , 161 :387–395
14. Umabala, P. Suresh, A. V. Prasadarao, Effective visible light photocatalytic degradation of brilliant green using H₂O₂ sensitized BiVO₄ , *M. journal of environmental protection*, 2012, 3: 1063-1069
15. Kyung-A Kim, Jae-Ryung Cha, Myoung-Seon Gong and Jong-Gyu Kim, Preparation of ZnO₂ Nanoparticles Using Organometallic Zinc(II) Isobutylcarbamate in Organic Solvent, *Bulletin of Korean Chemical Society*,2014, Vol. 35:2 431-435
16. W. Chen, Y. H. Lu, M. Wang, L. Kroner, H. Paul, H.-J. Fecht, J. Bednarcik, K. Stahl, Z. L. Zhang, U. Wiedwald, U. Kaiser, P. Ziemann, T. Kikegawa, C. D. Wu, and J. Z. Jiang, Synthesis, Thermal Stability and Properties of ZnO₂ Nanoparticles, *v.f. J. Phys. Chem. C* 2009, 113: 1320–1324
17. Liora Rosenthal-toib, Keren Zohar, Meital Alagem, Yoed Tsur, Synthesis of stabilized nanoparticles of zinc peroxide, *chemical engineering journal*,2008,136:425–429
18. Derle Shilpa G., Patil Niranjana P., Gaikwad Vishwas, Ecofriendly biodegradation of reactive yellow 145 by newly isolated bacillus boroniphilus from industrial effluent, *Journal of environmental research and development .journal of environmental research and development*, 2012,7:303-311
19. Li Yun Yang, Gui Peng Feng , Tian Xi Wang, Green synthesis of ZnO₂ nanoparticles from hydrozincite and hydrogen peroxide at room temperature, *Materials Letters* ,2010, 64: 1647–1649
20. Harish Kumar, Renu Rani, Structural and Optical Characterization of ZnO Nanoparticles Synthesized by Microemulsion Route, *International Letters of Chemistry, Physics and Astronomy*, 2013, 14:26-36.
21. S. Cheng, D. Yan, J. T. Chen, R. F. Zhuo, J. J. Feng, H. J. Li, H. T. Feng, and P. X. Yan, Soft-Template Synthesis and Characterization of ZnO₂ and ZnO Hollow Spheres, *J. Phys. Chem. C* ,2009, 113:13630–13635
22. Rauf, M.A., Salman Ashraf, S., fundamental principles and application of heterogeneous photocatalytic degradation of dyes in solution, *chemical engineering journal*,2009,151:10-18.
