

## Wear Behaviour of Hybrid Composite of Basalt Fiber with Titanium Oxide, Barium Sulphate and Silicon Carbide

T. Narendiranath Babu<sup>1\*</sup>, Ditto Ramesh<sup>2</sup>, D. Rama Prabha<sup>3</sup>, T. Lavanya<sup>4</sup>

<sup>1,2</sup>School of Mechanical and Building Sciences, VIT University, Vellore, India

<sup>3</sup>School of Electrical Engineering, VIT University, Vellore, India

<sup>4</sup>Department of Electrical and Electronics Engineering, DhanalakshmiSrinivasan Engineering College, Perambalur, India

**Abstract:** Today a significant growth is observed in the manufacturing of composite materials. Intensively developed polymer composite materials (PCM) are used in different sectors of industry and technology. They are successfully replacing traditional construction materials and also permit the conditions that exclude use of metals. By industrial production of basalt fibers on the basis of new technologies their cost is equal and even less than cost of glass fiber, moreover basalt fibers and materials on their basis have the most preferable parameter, a ratio of quality and the price in comparison with glass & carbon fibers, and other types of fibers. Though Basalt fiber has good wear resistance still increasing the wear resistance, decreasing friction coefficient, and increasing the hardness also gives more applications to basalt fiber like car brakes, interior decorations, car headliner, etc. more over increase in basalt fiber's tensile strength will give more applications to basalt fiber like bridges, underground tunnels, etc. From the results, it can be concluded that adding titanium oxide, silicon carbide and barium sulphate to the fiber matrix shows the increase in the above said properties, thus the above said mixture are added to the basalt fiber. The wear testing was conducted on the Pin on disc machine to predict the performance of material.

**Keywords:** Basalt fiber, wear behavior, pin on disc machine, wear resistance.

### 1. Introduction

Hybridization is a commonly used procedure to obtain properties, which are intermediate between the two originating materials. Dealing with polymer composites, hybridization may result in a compromise between mechanical properties and cost to meet specified design requirements, as one of the reinforcements is usually cheaper than the other one. A number of studies have been performed recently, which suggest that mechanical properties can be possibly tailored using hybridization based on glass or basalt fiber laminates and including other natural (aiming at a more sustainable material) or synthetic fibers. In particular, with respect to plant fibers, which equally show thermal and acoustic insulation properties, the higher specific weight of basalt fibers (around 2700 kg/m<sup>3</sup>) is widely compensated by their higher modulus, excellent heat resistance, good resistance to chemical attack and low water absorption. This suggests that hybrid laminates, based on basalt fibers and plant fibers, and/or glass-plant fiber hybrid laminates, the latter being particularly studied when it comes to the need for sufficient impact resistance, may have some interest. This would possibly result in a more sustainable end-of-life scenario without substantially affecting the structural performance of the laminates.

As a matter of fact, hybridization of basalt fibers has been attempted with ceramic fibers, to provide improved hot wear resistance to friction materials, with high tensile strength fibers, such as carbon and aramid, and with glass fibers. In these cases, basalt provided an impact and environmental resistance superior to that



provided by the corresponding hybrids with glass fibers, coupled with a substantial reduction in costs, with respect to carbon and aramid fiber composites. In the case of basalt/Nylon fibers hybrid laminates, low tensile modulus of Nylon is improved by adding basalt fibers, whilst Nylon provides conversely a higher impact resistance. Also basalt hybridization with glass fibers has been attempted, which is based on the use of two fibers, which are chemically not very different: continuous basalt fiber has a not very different content in silica and alumina from glass fibers and also a comparable, if not superior, tensile strength[1].

Though Basalt fibers tensile strength is higher than other fibers but still increase in basalt fiber's tensile strength will give more applications to basalt fiber like post-earthquake strengthening, bridges, underground tunnels etc. Moreover reducing the wear resistance, friction coefficient, and increasing the hardness also gives more applications to basalt fiber. Thus to increase its tensile strength we are adding Titanium oxide and Aluminium oxide to basalt fiber in proportion of 5% weight[3]. We are also adding Barium sulphate to basalt fiber in 5wt%, we are also adding Silicon carbide in 5wt% to increase the hardness[2] and we are also adding 2wt% of graphite to reduce coefficient of friction[4].

Basalt originates from volcanic magma and flood volcanoes, a very hot fluid or semifluid material under the earth's crust, solidified in the open air. Basalt is a common term used for a variety of volcanic rocks, which are gray, dark in colour, formed from the molten lava after solidification. Basalt rock-beds with a thickness of as high as 200 m have been found in the East Asian countries. Russia has unlimited basalt reserves. There are large deposits of these rocks in the Ural, Kam, chatka, Far East, Sakhalin, Kola Peninsula, Northwest Siberia, and the Transcaucasia. Basalt fiber is a material made from extremely fine fibers of basalt, which is composed of the minerals plagioclase, pyroxene, and olivine. Plagioclase is an important series of minerals within the feldspar family. The pyroxenes are a group of important rock-forming inosilicate minerals found in many igneous and metamorphic rocks. In silicates (from Greek, fiber), or chain silicates, have interlocking chains of silicate tetrahedra with either SiO<sub>3</sub>, 1:3 ratio, for single chains or Si<sub>4</sub>O<sub>11</sub>, 4:11 ratio, for double chains. Igneous rock is formed through the cooling and solidification of magma or lava.

Metamorphic rock is the result of the transformation of an existing rock type, the protolith, in a process called metamorphism, which means "change in form". The mineral olivine is a magnesium iron silicate with the formula (Mg,Fe)<sub>2</sub>SiO<sub>4</sub>. The mineral levels and chemical makeup of basalt formations can differ significantly from location to location. Moreover, the rate of cooling, when the original flow reached the earth's surface, also influenced the crystal structure. Its ready availability from mines and open-air quarries around the world, only a few dozen locations contain basalt that has been analyzed and qualified as suitable for manufacture of continuous thin filaments. Basalt formations in the Ukraine are particularly well suited to fiber processing.

Basalt Rock fibers have no toxic reaction with air or water, are non-combustible and explosion proof. When in contact with other chemicals they produce no chemical reactions that may damage health or the environment. It has good hardness and thermal properties, can have various application as construction materials. Basalt is a major replacement to the asbestos, which poses health hazards by damaging respiratory systems. Basalt base composites can replace steel (1 kg of basalt reinforces equals 9.6 kg of steel) as light weight concrete can be get from basalt fiber. As it is made of basalt rock is really cheap and has several excellent properties[5-7]. The major advantages of Basalt fiber are

- 20-25% higher tensile strength than E-glass [8]
- 10-15 % higher tensile modulus than E-glass [9]
- Better chemical resistance than regular E-glass
- Extended temperature range up to 580°C
- Environmental friendliness and easy recycling/disposal of basalt-fiber-reinforced plastics (BFRP) compared to GFRP [10]

The main objective of the paper is to increase the tensile strength, hardness, wear resistance and decrease friction coefficient. Thus it will be used in many applications like post-earthquake strengthening, bridges, underground tunnels etc. Moreover basalt fiber is cheap when compared to glass fibers, thus if this purpose is satisfied this can bring a new revolution in the composites. The main purpose of the paper is to produce a composite with basalt fiber as the core material and adding other materials like aluminium oxide, titanium oxide, Barium sulphate, silicon carbide and graphite to form a composite which has more tensile



strength than basalt fiber, higher wear resistance than basalt fiber, lower coefficient of friction and higher hardness.

## 2. Experimental

### Fabrication Process

1. The major component of basaltfiber is Epoxy LY556 (Resin).
2. Hardener HY951 is used for hardening and support.
3. Resin + Hardener are mixed in the ratio of 10:1 and the mixture made up is called MATRIX.
4. Tool is prepared by standard method.
5. Apply the matrix on glass cloth which is wrapped around the mandrel.
6. Ensure proper weighing is done.
7. Clamp the tool die for 2 hrs at ambient temperature condition.
8. The sample is then furnace heated at 100celcius for 2 hrs for hardening.
9. Take out and cool the specimen until room temp. is achieved.
10. Flash is removed from the sample.
11. Demoulding i.e. clamp is removed from the specimen.
12. Cut to appropriate dimension as per experimental needs
13. Emery paper of grade 60 is used to provide necessary surface finish.

The Figure1, Figure 2 and Figure 3 shows the basaltfiber, mould cavity and hot air oven for preparing specimen.



Figure 1.Basalt Fiber



Figure 2.Mould Cavity

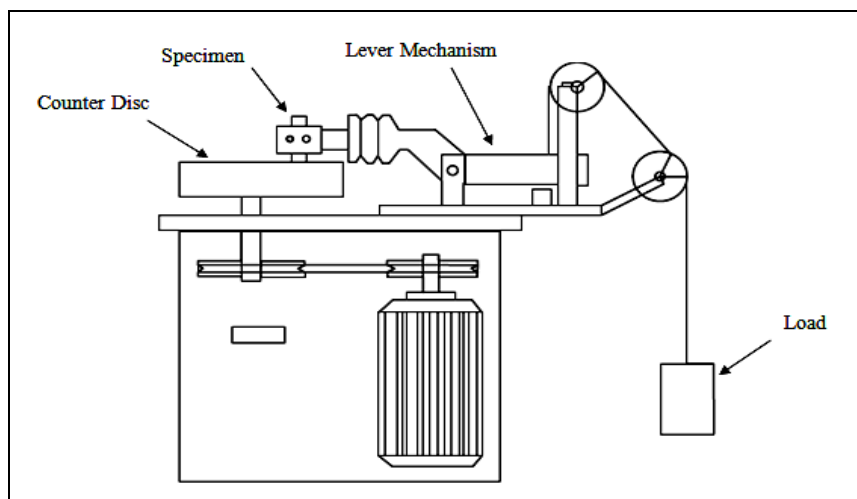


Figure 3. Hot Air Oven

### 3. Experimental Setup

This test method describes a laboratory procedure for determining the wear of materials during sliding using a pin-on-disc test rig shown in Figure 4. Materials are tested in pairs under nominally non-abrasive conditions. A pin on disc is an instrument that measures tribological quantity, such wear behaviour, between two surfaces in contact. Table 1 shows test rig parameters.





**Figure 4. Pin-on-Disc Test Rig**

**Table 1 Test Rig Parameters**

S.No	Description	Details
1	Speed	Min 200 rpm, max 2000 rpm
2	Normal Load	200N max
3	Frictional Force	200N max
4	Wear	$\pm 2\text{mm}$
5	Wear Track Diameter	Min 50mm, max 100mm
6	Sliding Speed	Min 0.3m/sec, max 10m/sec
7	Preset Timer	99/59/59 hr/min/sec
8	Specification Size (Pin)	$\varnothing 3,4,5,6,8,10$ & 12mm
9	Wear Disc Size	Dia 165mm X 8mm Thick, EN-31 Hardened To 60hrc, Ground To Surface Roughness 1.6Ra
10	Environmental Chamber	This chamber prevents oil spillage and collects debris after test
11	Software	Winducom 2010
12	Software Interface	Comport

### 3.1 Procedure

A pin-on-disc test setup was used for slide wear experiments. The surface of the sample (5mm X 5 mm) glued to a pin of dimensions 10 mm diameter and 30 mm length comes incontact with a hardened disc of hardness 60 HRC. The counter surface disc was made of En31 steel having dimensions of 165 mm diameter, 8 mm thick and surface roughness (Ra) of  $1.6\text{ }\mu\text{m}$ . The test was conducted on a track of 115 mm diameter for a specified test duration,load and velocity. Prior to testing, the test samples were rubbed against a 600-grade SiCpaper. The surfaces of both the sample and the disc were cleaned with a soft paper soaked inacetone before the test. The pin assembly was initially weighed using a digital electronicbalance (0.1 mg accuracy). The test was carried out by applying normal load at different sliding velocities. At the end of the test, the pin assembly was again weighed in the same balance. A minimumof three trials was conducted to ensure repeatability of test data. The friction force at thesliding interface of the specimen was measured at an interval of 5 minutes using a frictionalload cell. The coefficient of friction was obtained by dividing the frictional force by theapplied normal force.The aim in the first group is to investigate the effect ofload and velocity on tribologicalbehaviours. The bearing velocities are kept in between 2.5-3 m/s and the bearing loading upto9 kgf.



## 4. Results and Discussion

The main objective of the paper is to increase the tensile strength, increase the hardness, increase the wear resistance and decrease the friction co efficient. Thus from the literature survey, a suitable solution has been proposed. The following materials are added to the basalt fiber,

- Titanium oxide
- Barium Sulphate
- Silicon carbide
- Graphite

The above given materials are added to the Basalt fiber in the given weight proportion. The figure 5 shows wear test specimen.

### 4.1 Specimen composition

Different samples prepared are :

- Sample 1
  - Basalt fiber – 40%
  - Epoxy Resin – 60%
- Sample 2
  - Basalt fiber – 23%
  - Titanium oxide – 5%
  - Silicon carbide – 5%
  - Barium sulphate – 5%
  - Graphite – 2%
  - Epoxy Resin – 60%
- Sample 3
  - Basalt fiber – 50%
  - Epoxy Resin – 50%
- Sample 4
  - Basalt fiber – 33%
  - Titanium oxide – 5%
  - Silicon carbide – 5%
  - Barium sulphate – 5%
  - Graphite – 2%
  - Epoxy Resin – 50%
- Sample 5
  - Basalt fiber – 50%
  - Aluminum oxide – 5%
  - Titanium oxide – 5%
  - Silicon oxide – 5%
  - Epoxy resin – 35%



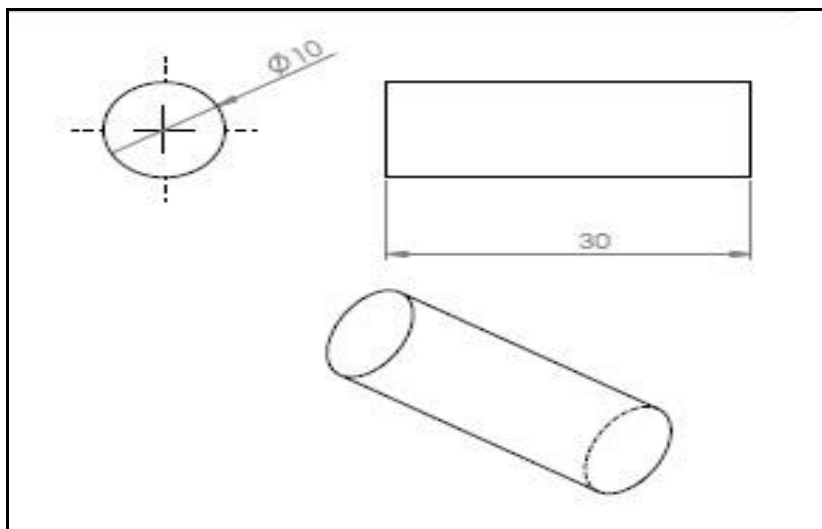


Figure 5 Wear test specimen

#### 4.2. Pin on Disc Wear Test Result :

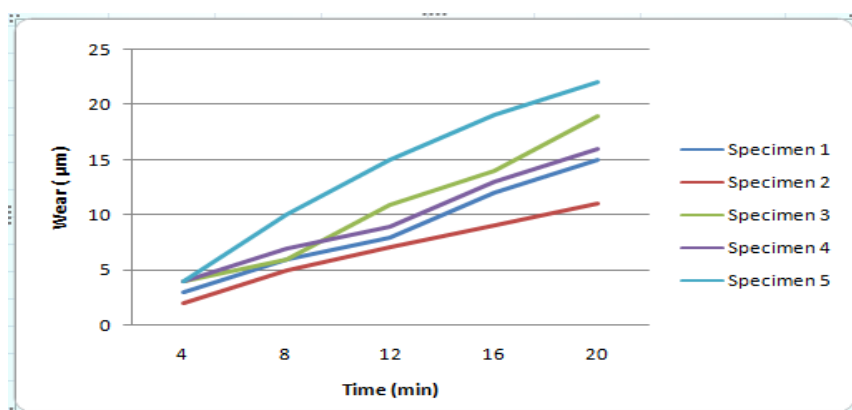


Figure 6. Wear test at 700rpm and 3kgf load


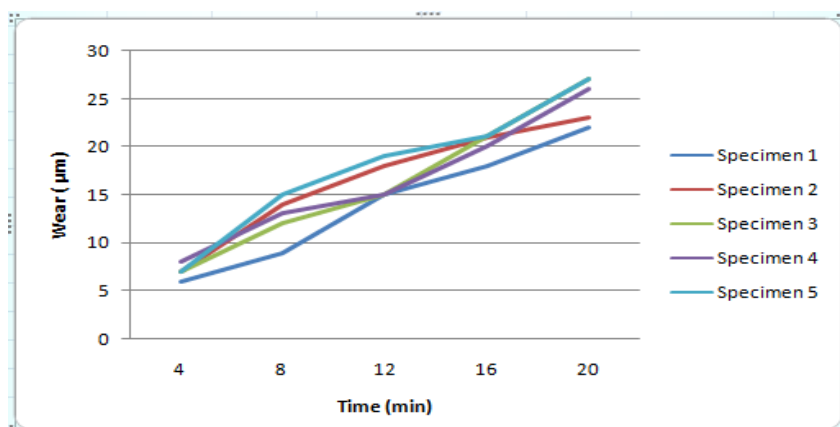


Figure 7. Wear test at 700rpm and 6kgf load




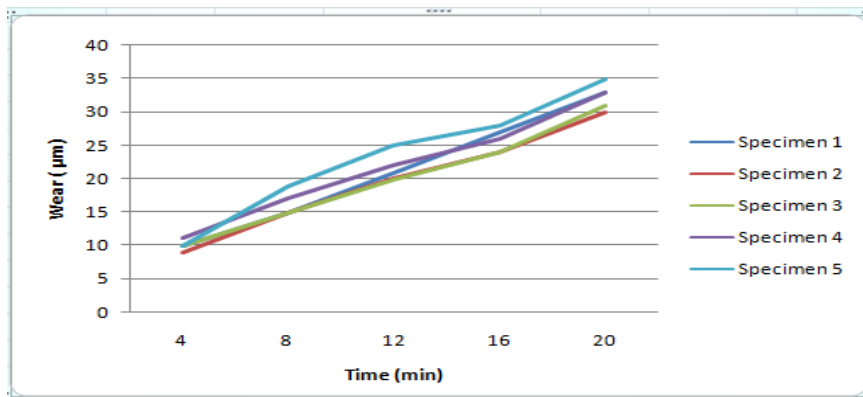


**Figure 8. Wear test at 700rpm and 9kgf load**

From Figure 6-8 the following results were observed

- It is seen that specimen 1 has highest wear at 700 rpm for different load applied
- Wear gradually reduces from specimen 5,specimen 3
- least wear goes to specimen 2
- specimen 2 has a minimum wear of 30 micro meter for a maximum load of 9 kgf running to a period of 20 min which is very minimum it can be used in applications where friction is more

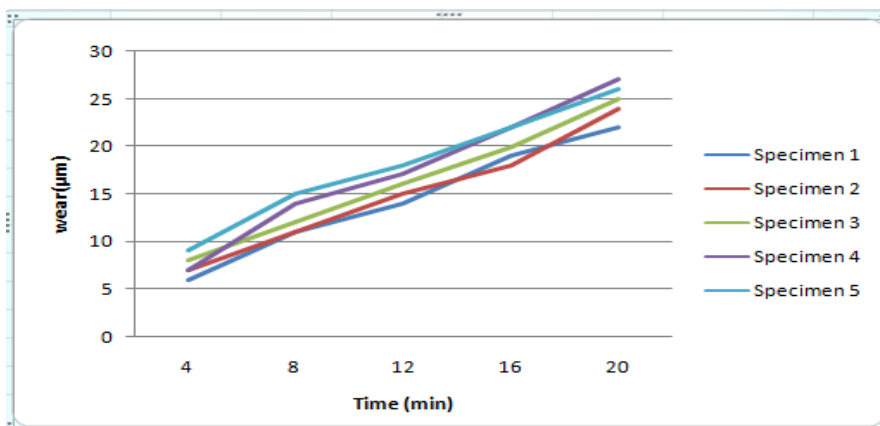


**Figure 9. Wear test at 800 rpm and 3kgf load**

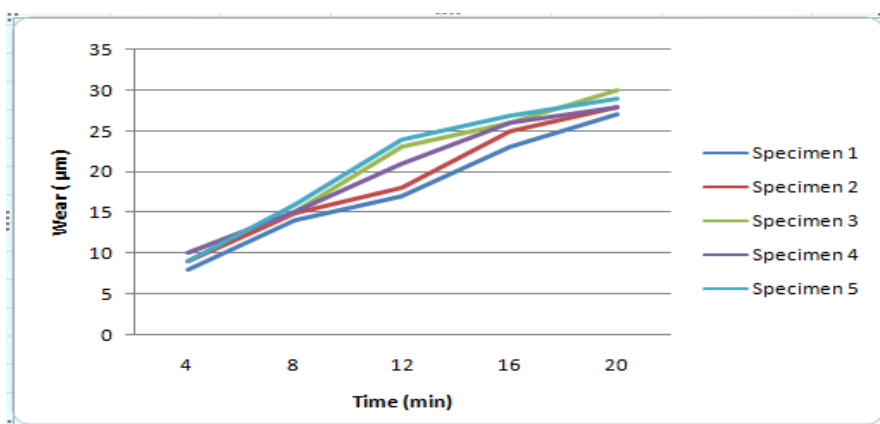

**Figure 10. Wear test at 800 rpm and 6kgf load**




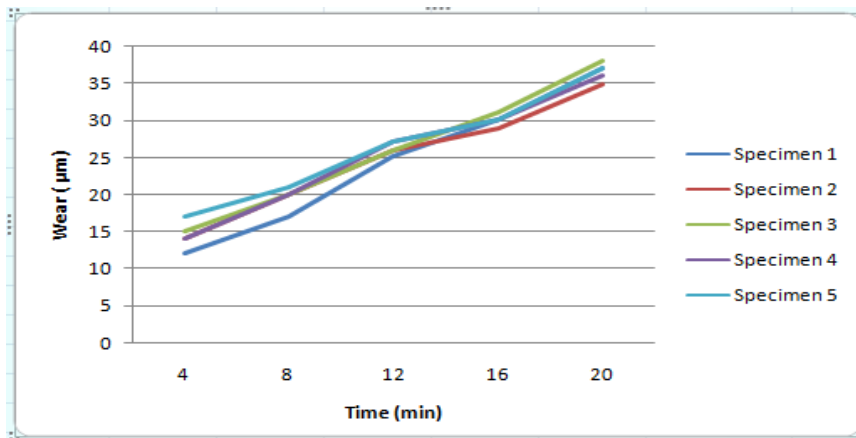


**Figure 11. Wear test at 800 rpm and 9kgf load**

From Figure 9-11 the following results were observed

- As the speed increases from 700 to 800 rpm wear rate also increases in each specimen irrespective of the load applied when compared with that of 700 rpm
- Specimen 3 has the maximum average wear for different load applied
- Specimen 2 has least wear with maximum load of 9 kgf
- Remaining specimen has the intermidate wear in the decending order from specimen 5,specimen 4, specimen 3

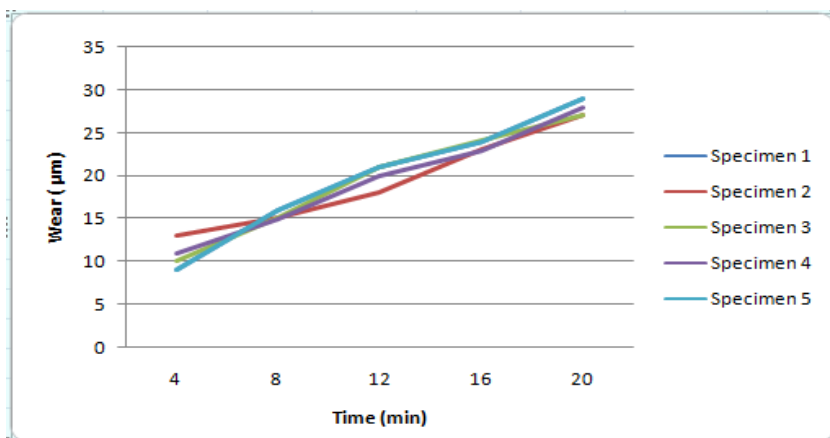


**Figure 12. Wear test at 900 rpm and 3kgf load**

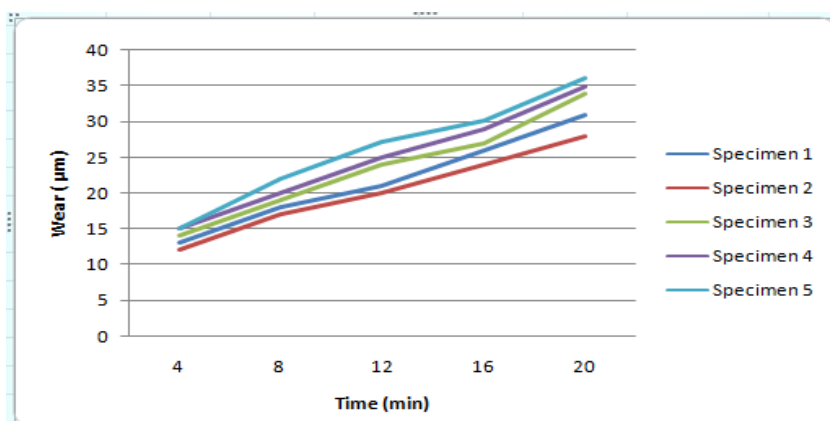

**Figure 13. Wear test at 900 rpm and 6kgf load**



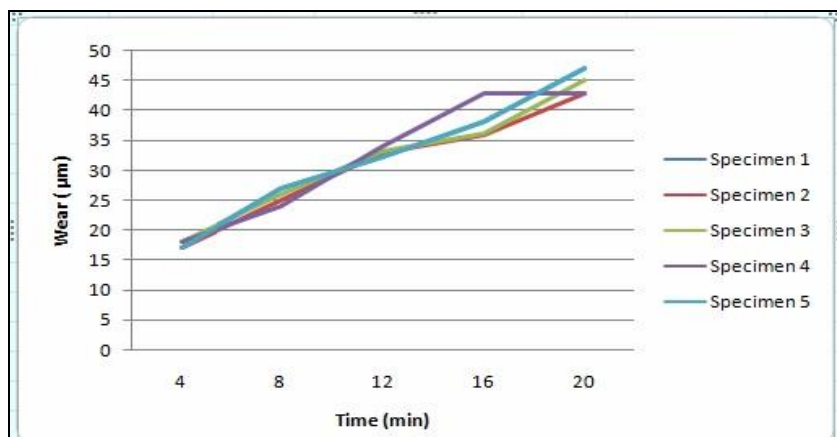

**Figure 14. Wear test at 900 rpm and 9kgf load**

From Figure 12-14 the following results were observed

- As the speed increases from 800 to 900 rpm wear rate also increases in each specimen irrespective of the load applied when compared with that of 700 and 800 rpm
- Specimen 5 has the maximum average wear for different load applied
- Specimen 2 has least wear with maximum load of 9 kgf
- Remaining specimen has the intermediate wear in the descending order from specimen 1, specimen 4, specimen

## 5. Conclusion

The wear rate of specimen 1 is the highest among the specimens for 700 rpm and it gradually increases and maintains the same wear rate at increasing the speed and load. Specimen 1 has moderate coefficient of friction as compared to other specimens, thus it can be used in applications where coefficient of friction is neither high nor low is required. Thus specimen is a moderate sample with not so high and not so low properties, thus it can be used in applications where friction is not very high or not very low is required with medium hardness.

The wear rate of specimen 2 is the lowest and thus it can be used in applications where wear rate is high. Specimen 2 has less coefficient of friction as compared to other specimens, thus it can be used in applications where coefficient of friction is less required. Thus specimen 2 can be used in applications where high tensile strength and hardness is required, low friction coefficient and, low wear rate. Thus the purpose of the paper of increasing the tensile strength, hardness, wears resistance and decreasing the coefficient of friction has been achieved. The specimen 2 has satisfied with good tribological performance.

## 6. References

1. A short Review on Basalt Fiber by Kunal Singha International Journal of textile science, 2012, 1(4): 19-28.
2. Wei B, Song S, Cao H. Strengthening of basalt fibers with SiO<sub>2</sub>- epoxy composite coating, Mater Des 2011: 32:4180-6.
3. Fabrication and characterization of TiO<sub>2</sub> particulate filled Glass Fiber reinforced polymer composite, S. Srinivasa Moorthy, K. Manonmani (2013)
4. The effect of sintering and sintering techniques on mechanical properties of Cu-graphite metal matrix composite prepared by powder metallurgy route C.P. Samal, J.S. Paihar, D. Chaira (2013)
5. A review on basalt fiber and its composites, V.Fiorel, T. Scalicil, G. Di Bella<sup>2</sup>, A. Valenzal (2014)
6. Abrasion resistance and fracture energy of concretes with basalt fiber, Nihat Kabay, Yildiz Technical University, Department of civil Engineering (2013).



7. Mechanical characterisation of hybrid composite laminates based on basalt fibers in combination with flax, hemp and glass fibers manufactured by vacuum infusion, R. Petrucci, C. Santulli b, D. Puglia a, F.Sarasini b , L. Torre a, J.M. Kenny
8. Hancock, Paul and Skinner, Brian J. "basalt". The Oxford companion to the Earth, 2000.
9. "Continuos basalt fiber sector in shaping. (Statistics)" China Chemical Reporter. July 6, 2010.
10. Palmieri, A., Matthys S, and Tierens, M. "Basalt fibers: Mechanical properties and applications for concrete structures." Taylor and Francis Group. 2009.

\*\*\*\*\*



# International Journal of ChemTech Research

[\[www.sphinxssai.com\]](http://www.sphinxssai.com)

Publish your paper in Elsevier Ranked, SCOPUS Indexed Journal.

[1] RANKING:

has been ranked NO. 1. Journal from India (subject: Chemical Engineering) from India at International platform, by SCOPUS- scimagojr.

It has topped in total number of CITES AND CITABLE DOCUMENTS.

Find more by clicking on Elsevier- SCOPUS SITE....AS BELOW.....

[http://www.scimagojr.com/journalrank.php?area=1500&category=1501&country=IN&year=2011&order=cd&min=0&min\\_type=cd](http://www.scimagojr.com/journalrank.php?area=1500&category=1501&country=IN&year=2011&order=cd&min=0&min_type=cd)

Please log on to - [www.sphinxssai.com](http://www.sphinxssai.com)

[2] Indexing and Abstracting.

International Journal of ChemTech Research is selected by -

CABI, CAS(USA), **SCOPUS**, MAPA (India), ISA(India),DOAJ(USA),Index Copernicus, Embase database, EVISA, DATA BASE(Europe), Birmingham Public Library, Birmingham, Alabama, RGATE Databases/organizations for Indexing and Abstracting.

It is also in process for inclusion in various other databases/libraries.

[3] Editorial across the world. [4] Authors across the world:

For paper search, use of References, Cites, use of contents etc in-

International Journal of ChemTech Research,

Please log on to - [www.sphinxssai.com](http://www.sphinxssai.com)

\*\*\*\*\*